



## Numerical investigation of perforated aluminium tubes with different types of geometrical discontinuities under bending

Çetin Karakaya<sup>1</sup>, Seçil Ekşi<sup>2\*</sup>

<sup>1</sup> Independent Researcher, Hastings, United Kingdom

Email: [cetkarakaya@gmail.com](mailto:cetkarakaya@gmail.com) - ORCID:0000-0002-9227-9170

<sup>2</sup>Mechanical Engineering Department, Sakarya University, Sakarya, 54050, Turkey

\* Corresponding Author Email: [eksi@sakarya.edu.tr](mailto:eksi@sakarya.edu.tr) - ORCID: 0000-0002-1404-718X

### Article Info:

DOI: 10.22399/ijcesn.2237

Received : 21 March 2025

Accepted : 05 May 2025

### Keywords :

Aluminum, Bending  
Perforated tube  
Hole shape  
Finite element analysis

### Abstract:

In this study, the effect of hole shape on the bending behavior of aluminum 6063-T5 tubes was investigated numerically. The effects of hole geometries in the form of circles, triangles, squares, hexagons, ellipses, and diamonds on the bending behavior of the tube structure were investigated by finite element analysis. As a result of the analysis, the tube structure with the highest load-carrying and energy-absorption capacity is the ellipse perforated tube. In terms of specific load carrying and specific energy absorption capacity, the ellipse perforated tube structure is again in first place. Compared to the non-perforated tube, the load carrying capacity has decreased by 13.6%, and the energy absorption capacity has decreased by 11%. The triangular perforated structure comes in second place. The square perforated tube is in last place.

### 1. Introduction

Lightweight, energy-efficient structural components are increasingly essential in transportation, aerospace, and defense industries, where weight reduction must be balanced with structural integrity and crashworthiness. Thin-walled aluminum tubes, owing to their excellent strength-to-weight ratio, corrosion resistance, and formability, have been extensively studied for applications in energy absorption systems, crash boxes, and structural frames [1–3]. While the mechanical behavior of such tubes under axial compression is well-documented [4–6], the response under bending, especially in the presence of perforations, remains a relatively underexplored field.

Bending loads are prevalent in real-world applications, such as side impacts in automotive collisions or bending architectural support elements. Under such loading, thin-walled tubes exhibit complex deformation mechanisms, including ovalization, local buckling, and plastic hinge formation [7–9]. These failure modes are susceptible to the geometry, material properties, and loading conditions [10–12]. Perforations, introduced either for functional purposes (e.g., ventilation, wiring) or as a design strategy for controlled collapse, further

complicate this response by altering stiffness, stress distribution, and buckling patterns [13–15].

The integration of holes in tube structures has been studied with growing interest, particularly in axial and lateral crushing. Previous studies have shown that introducing geometric discontinuities such as holes and grooves can significantly influence crushing behavior and energy absorption performance. For instance, Montazeri et al. investigated the energy absorption, specific energy absorption (SEA), and crushing performance of holed and grooved thin-walled tubes under axial loading, demonstrating that geometric modifications can effectively tailor deformation modes and improve crash performance [16]. Similarly, Taghipoor et al. examined square thin-walled tubes with circular hole discontinuities under high-speed impact loading and reported notable changes in crashworthiness indicators depending on hole configuration and impact conditions [17]. Earlier experimental work by Cheng et al. focused on AA6061-T6 aluminum square tubes with various through-hole discontinuities, revealing that hole type and arrangement significantly affect crush behavior and deformation mechanisms. These studies collectively highlight the importance of controlled geometric discontinuities in optimizing the

crashworthiness performance of thin-walled energy absorbers [18]. More recently, Elyasi and Modanloo investigated perforated AA6061-O tubes with irregular hole geometries under axial compression, emphasizing the role of hole irregularity in optimizing crushing performance and improving energy absorption efficiency. Collectively, these studies underline the critical role of geometric discontinuities in tailoring the crashworthiness performance of thin-walled aluminum structures [19].

Several researchers have explored foam-filled, multi-cell, and triggered geometries to enhance energy dissipation [20-22]. However, perforated tubes offer a passive and potentially lighter-weight alternative, with design tunability via hole size, shape, and layout. Beyond conventional perforation patterns, Rouzegar et al. investigated the axial crushing response of perforated metal and composite-metal hybrid tubes, highlighting the interaction between material composition and perforation geometry on energy dissipation capacity [23]. Mohamed Ismail conducted a comprehensive performance analysis and optimization study on square tubes with varying hole shapes, sizes, and patterns under axial compression, demonstrating that hole configuration plays a critical role in balancing peak crushing force and energy absorption efficiency. Collectively, these studies confirm that controlled perforation design is a key parameter in tailoring deformation mechanisms and improving the crashworthiness performance of thin-walled tubular structures [24].

When existing studies are examined, the combined effect of these parameters with different hole types, such as circular, square, elliptical, or hexagonal holes, remains an open question. The lack of systematic numerical research on these parameters under bending motivated the current study. This study aims to systematically investigate the bending behavior of perforated aluminum tubes with varying hole shapes. In this study, the effect of hole shape on the bending behavior of aluminum 6063-T5 tubes was investigated numerically. The research employs finite element simulations to evaluate how perforation shapes influence bending strength, bending stiffness, load carrying capacity, and energy absorption capacity. Through this comprehensive approach, the work contributes to optimizing perforated tube designs for lightweight and crashworthy applications in transportation and structural engineering applications.

## 2. Validation Study

The tube used in the validation study in experiments is Al 6063-T5. The outer diameter is 31 mm, the wall thickness is 1 mm, and the length of the cylindrical aluminum tube is 270 mm, respectively. The material used for the tube is Al 6063-T5 with the following properties: mass density  $\rho = 2.7 \text{ g} \times \text{cm}^{-3}$ , Young's modulus  $E = 69 \text{ GPa}$ , yield strength  $\sigma_Y = 187 \text{ MPa}$ , ultimate stress  $\sigma_U = 247 \text{ MPa}$ , Poisson's ratio  $\nu = 0.33$ . A tensile test for the aluminum tube was carried out using specimens prepared according to the ASTM E8 standard. A video extensometer was used in tension test programs. Three-point bending tests were carried out on a 10 kN bending test machine to determine the bending behavior of tubes. The diameter of the punch and supports was set to be 30 mm, which was suitable for the tube diameter. The span of the two supports was 217 mm. The loading rate was kept constant at  $0.5 \text{ mm} \times \text{s}^{-1}$ .

The finite element model is generated and analyzed using ANSYS. In this model, the full model was generated without using symmetry assumptions, which resulted in 10371 3-D 20-node solid elements (Solid186) and 63005 nodes for the tubular beam, supports, and the loading punch. Since the problem involves large deformation, the nonlinear geometry is also turned on during the analysis. The coefficient of friction between the contacting surfaces is taken as  $\sigma = 0.2$ . Figure 2 represents load-displacement curves from the experiment and finite element simulations. The load magnitudes between the experiment and simulation differ by  $\sim 1.5 \%$ . From the above comparison, it is clear that the finite element model and simulation methodology used are valid, and therefore, the method and similar models can be used to study the behavior of other similar systems for different material properties. Figure 1 shows the experimental setup used for the three-point bending test and the finite element analysis model.

## 3. Numerical Study

Material properties and the dimensions of the tube structure used in finite element analyses are the same as the tube used in the validation study. The outer diameter is 31 mm, the wall thickness is 1 mm, and the length of the cylindrical aluminum tube is 270 mm, respectively. The span of the two supports was 217 mm. The diameter of the punch and supports was 30 mm.

The finite element models are generated and analyzed using ANSYS. The finite element analysis model of the perforated tubes with circular hole shape is shown in Figure 3. Hole shapes for perforated tubes are given in Figure 4.

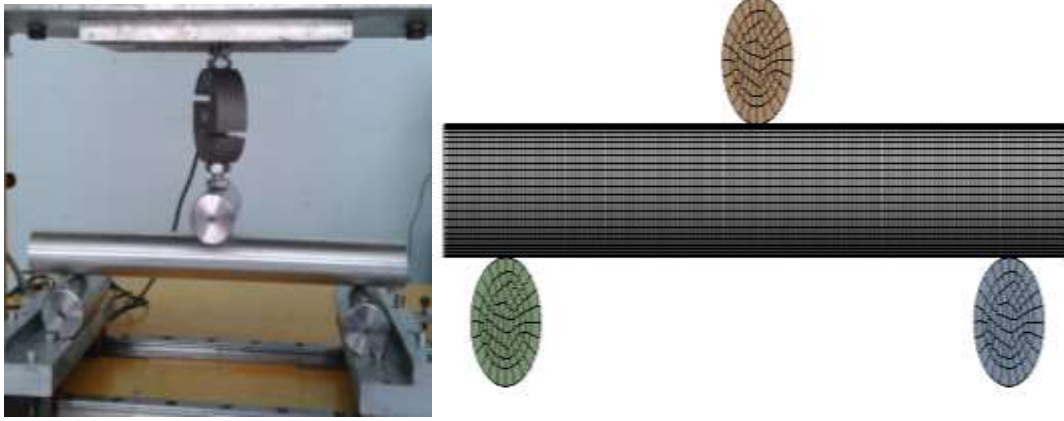


Figure 1. a) Experimental set-up for three-point bending validation test, b) Finite element analysis model

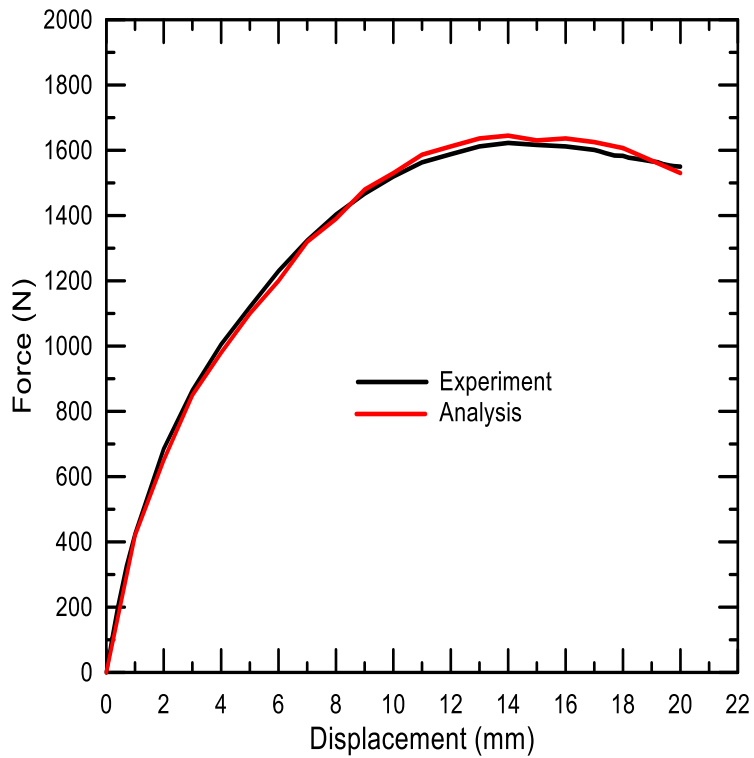


Figure 2. Force-displacement curves from the experiment and finite element simulation

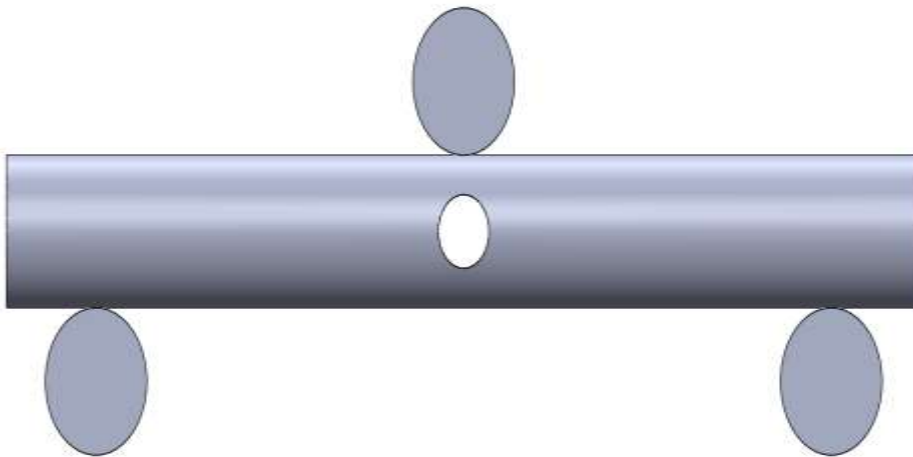


Figure 3. Finite element analysis models of perforated tubes

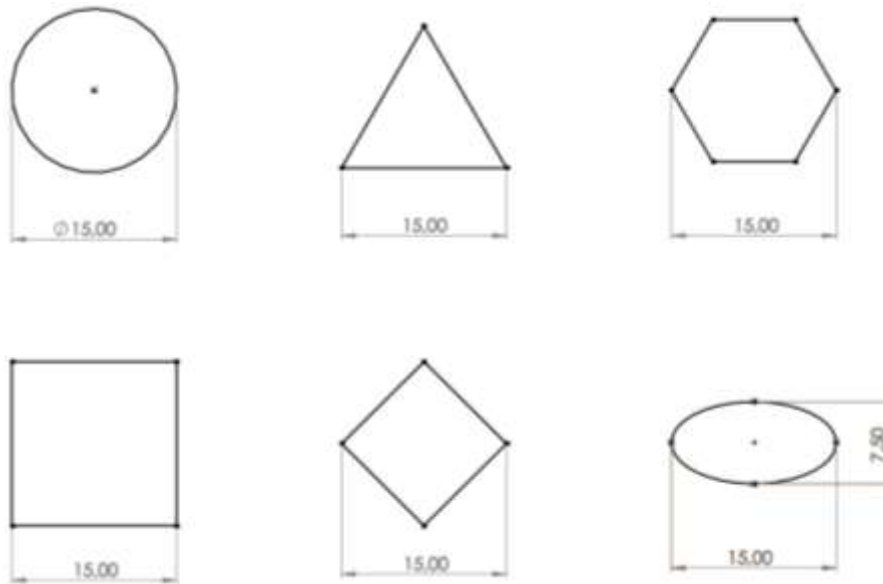


Figure 4. Hole shapes for a perforated tube

To investigate the performance of tube structures under three-point bending, four parameters - load carrying capacity (LC), specific load carrying capacity (SLC), energy absorption (EA), and specific energy absorption (SEA) are evaluated. This study uses these four parameters in tubes with different hole shapes. The highest force developed by the structure is known as the load-carrying capacity or LC. Considering the force-displacement curve, EA represents the energy the tube structure absorbs for a given displacement value. Therefore, EA can be explained as follows:

$$EA = \int_0^d F(y) dy \tag{1}$$

Where  $F(y)$  is the instantaneous load the tube structure carries, and  $d$  is the bending displacement. The specific energy absorption (SEA) is defined as the ratio of the energy absorbed by a structure to its mass, as presented in Eq. (2). In Eq. (2),  $m$  is the mass of the extrusion structure. This is a valid quantitative parameter, especially when comparing the performances of energy absorbers with different masses and geometries:

$$SEA = \frac{EA}{m} \tag{2}$$

#### 4. Results and Discussions

Figure 5 compares the tubes' force (N) - displacement (mm) performances with different geometric hole shapes. Figure 5 presents the load-

displacement responses of aluminum tubes with and without perforations under bending conditions. The black curve represents the tube without holes, serving as a baseline for comparison. In contrast, the colored curves correspond to tubes with perforations of different geometrical shapes: triangle, circle, square, hexagon, horizontal ellipse, and diamond. As expected, the tube without holes exhibits the highest peak load, indicating superior structural integrity. This confirms that the introduction of perforations leads to a reduction in load-carrying capacity due to the localized stress concentrations and material removal. Among the perforated configurations, the tube with elliptical holes demonstrates the highest peak force, followed closely by the triangular hole configuration. These two geometries maintain a relatively high load-bearing capacity, suggesting a more favorable stress distribution around the perforations. The circular and hexagon configurations show intermediate performance. In contrast, the square and diamond hole configurations result in the most significant reduction in peak force, with the circular hole configuration exhibiting the lowest load capacity. These shapes may cause more severe stress concentrations and material weakening under bending loads. Overall, the results indicate that the geometry of perforations plays a critical role in the structural response of tubes under bending. While perforations are often necessary for weight reduction or functional purposes, selecting an optimal hole shape, such as the horizontal ellipse or triangle, can mitigate strength degradation. Simulation results obtained from finite element analyses are given in Table 2.

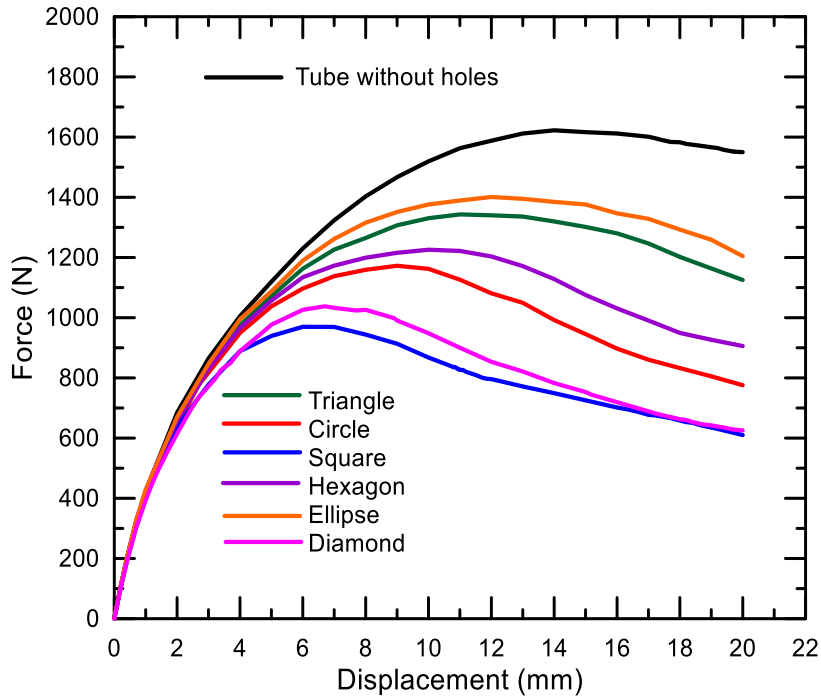


Figure 5. Force-displacement curves of tubes with various hole shapes

Table 2. Simulation results obtained from finite element analyses (<sup>a</sup>Energy values are calculated up to 20 mm displacement)

Specimen type	F <sub>max</sub> (LC) (N)	Weight (g)	Specific load capacity (SLC) (N.g <sup>-1</sup> )	Energy <sup>a</sup> (J) (EA)	Specific absorbed energy (SEA) (J.g <sup>-1</sup> )
Tube without hole	1622	68.71	23,61	26.20	0,38
Triangle	1343	68.17	19,70	22.37	0,33
Square	970	67.44	14,38	15.18	0,23
Circle	1172	67.71	17,31	18.60	0,27
Ellipse	1401	68.23	20,53	23.32	0,34
Hexagon	1225	67.89	18,04	20.05	0,30
Diamond	1039	67.43	15.40	15.83	0.23

The tube without a hole exhibits the highest values for maximum load (F<sub>max</sub>) and absorbed energy (Energy). It also shows the highest specific metrics (SLC and SEA).

Among the specimens with holes, the ellipse generally performs the best in terms of both load capacity and energy absorption. The square has the lowest values in nearly every category, making it the weakest performer overall. The tube without a hole has the highest F<sub>max</sub> (1622 N). The ellipse stands out among the shapes with holes (1401N), while the square has the lowest (970 N). SLC of the tube without a hole leads with 23.61 N/g, confirming its high strength-to-weight ratio. The ellipse follows at 20.53 N/g, and the triangles are close to each other in the mid-range. The square again is the lowest (14.38 N/g). The ellipse hole also absorbs the most energy (23.32 J). The triangle is next (22.37 J), with the square lowest (15.18 J). In terms of energy absorption per unit mass, the SEA of the ellipse still leads at 0.34 J/g. The Square and diamond remain the least efficient (0.23 J/g).

The von-Mises stress distribution of tubes with various hole shapes is shown in Figure 6. The tube (no hole) benefits from having no stress concentration zones, such as corners or openings, which helps distribute load evenly and enhances load capacity and energy absorption. Among the hollow shapes, the hexagon performs better than the shapes with fewer sides (Triangle, Square) or purely curved profiles (Circle, Ellipse), likely because of an effective stress distribution around its six edges and internal geometry. Shapes with sharp corners (Square, Triangle) typically introduce higher stress concentrations, explaining their lower load capacities and energy absorption values.

### 5. Conclusions

This paper presents a numerical investigation of the bending behavior of aluminum tubes with various hole shapes. The presence and shape of holes significantly affect the tube's structural strength. The best-performing perforated designs are those with

elliptical and triangular holes, while square holes cause the most significant drop in load capacity. If maintaining strength while reducing weight is a priority, choosing the proper hole shape is crucial. Even though all specimens have very similar weights, their ability to carry the load and absorb energy varies significantly. If the aim is to maximize

load carrying and energy absorption for a given weight, the ellipse perforated tube is the best choice among perforated tubes, followed by the triangular. The square is the least optimal choice here, showing the lowest load capacity and energy values.

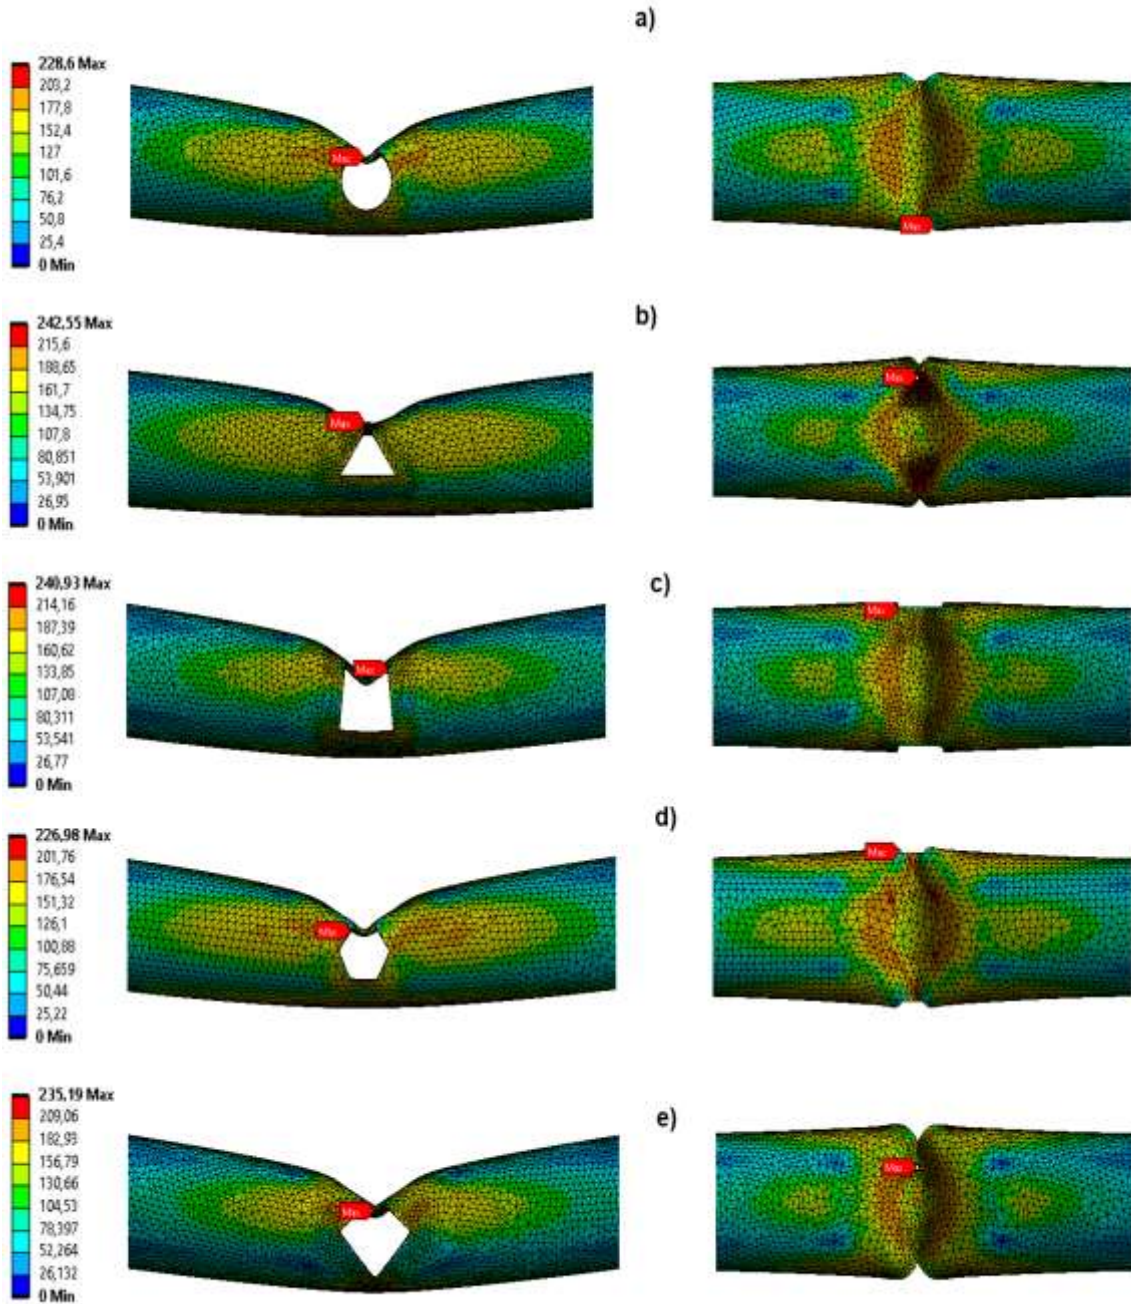


Figure 6. Von-Mises stress distributions of the tube with various hole shapes, a) circle, b) triangle, c) square, d) hexagon, e) diamond

**Author Statements:**

- **Ethical approval:** The conducted research is not related to either human or animal use.
- **Conflict of interest:** The authors declare that they have no known competing financial interests

- or personal relationships that could have appeared to influence the work reported in this paper
- **Acknowledgement:** The authors declare that they have nobody or no-company to acknowledge.

- **Author contributions:** The authors declare that they have equal right on this paper.
- **Funding information:** The authors declare that there is no funding to be acknowledged.
- **Data availability statement:** The data that support the findings of this study are available on request from the corresponding author. The data are not publicly available due to privacy or ethical restrictions.

## References

- [1] Abramowicz, W., & Jones, N. (1984). Dynamic axial crushing of circular tubes. *International Journal of Impact Engineering*, 2(3), 263–281. [https://doi.org/10.1016/0734-743X\(84\)90010-1](https://doi.org/10.1016/0734-743X(84)90010-1)
- [2] Hanssen, A. G., Langseth, M., & Hopperstad, O. S. (2000). Static and dynamic crushing of circular aluminium extrusions with aluminium foam filler. *International Journal of Impact Engineering*, 24(5), 475–507. [https://doi.org/10.1016/S0734-743X\(99\)00170-0](https://doi.org/10.1016/S0734-743X(99)00170-0)
- [3] Langseth, M., Hopperstad, O. S., & Berstad, T. (1999). Crashworthiness of aluminium extrusions: Validation of numerical simulation, effect of mass ratio and impact velocity. *International Journal of Impact Engineering*, 22(9–10), 829–854. [https://doi.org/10.1016/S0734-743X\(98\)00070-0](https://doi.org/10.1016/S0734-743X(98)00070-0)
- [4] Mamalis, A. G., Yuan, Y. B., & Viegelaahn, G. L. (1992). Collapse of thin-wall composite sections subjected to high speed axial loading. *International Journal of Vehicle Design*, 13(5–6), 564–579. <https://doi.org/10.1504/IJVD.1992.061748>
- [5] Thornton, P. H., & Jeryan, R. A. (1988). Crash energy management in composite automotive structures. *International Journal of Impact Engineering*, 7(2), 167–180. [https://doi.org/10.1016/0734-743X\(88\)90024-3](https://doi.org/10.1016/0734-743X(88)90024-3)
- [6] Abramowicz, W. (2003). Thin-walled structures as impact energy absorbers. *Thin-Walled Structures*, 41(2–3), 91–107. [https://doi.org/10.1016/S0263-8231\(02\)00082-4](https://doi.org/10.1016/S0263-8231(02)00082-4)
- [7] Kecman, D. (1983). Bending collapse of rectangular and square section tubes. *International Journal of Mechanical Sciences*, 25(9–10), 623–636. [https://doi.org/10.1016/0020-7403\(83\)90072-3](https://doi.org/10.1016/0020-7403(83)90072-3)
- [8] Wu, C., Wang, C., & Kim, J. W. (2021). Bending deformation prediction in a welded square thin-walled aluminum alloy tube structure using an artificial neural network. *The International Journal of Advanced Manufacturing Technology*, 117(9), 2791–2805. <https://doi.org/10.1007/s00170-021-07884-9>
- [9] Mirzaei, M., Shakeri, M., Sadighi, M., & Akbarshahi, H. (2012). Experimental and analytical assessment of axial crushing of circular hybrid tubes under quasi-static load. *Composite Structures*, 94(6), 1959–1966. <https://doi.org/10.1016/j.compstruct.2012.01.003>
- [10] Fan, D., Qi-hua, M., Xue-hui, G., & Tianjun, Z. (2021). Crashworthiness analysis of perforated metal/composite thin-walled structures under axial and oblique loading. *Polymer Composites*, 42(4), 2019–2036. <https://doi.org/10.1002/pc.25954>
- [11] Yang, K., Xu, S., Shen, J., Zhou, S., & Xie, Y. M. (2016). Energy absorption of thin-walled tubes with pre-folded origami patterns: Numerical simulation and experimental verification. *Thin-Walled Structures*, 103, 33–44. <https://doi.org/10.1016/j.tws.2016.02.007>
- [12] Reddy, B. D. (1979). An experimental study of the plastic buckling of circular cylinders in pure bending. *International Journal of Solids and Structures*, 15(9), 669–683. [https://doi.org/10.1016/0020-7683\(79\)90066-0](https://doi.org/10.1016/0020-7683(79)90066-0)
- [13] Rouzegar, J., Assaee, H., Elahi, S. M., & Asiaei, H. (2018). Axial crushing of perforated metal and composite-metal tubes. *Journal of the Brazilian Society of Mechanical Sciences and Engineering*, 40(7), 349. <https://doi.org/10.1007/s40430-018-1266-6>
- [14] Nawar, M. T., El-Zohairy, A., & Arafa, I. T. (2023). Finite element modeling and analysis of perforated steel members under blast loading. *Modelling*, 4(4), 628–649. <https://doi.org/10.3390/modelling4040036>
- [15] Alshahrani, H., Sebaey, T. A., Awd Allah, M. M., & Abd El-Baky, M. A. (2022). Quasi-static axial crushing performance of thin-walled tubes with circular hole discontinuities. *Journal of Composite Materials*, 56(27), 4195–4218. <https://doi.org/10.1177/00219983221129016>
- [16] Montazeri, S., Elyasi, M., & Moradpour, A. (2018). Investigating the energy absorption, SEA and crushing performance of holed and grooved thin-walled tubes under axial loading with different materials. *Thin-Walled Structures*, 131, 646–653. <https://doi.org/10.1016/j.tws.2018.07.024>
- [17] Taghipoor, H., Ghiaskar, A., & Shavalipour, A. (2022). Crashworthiness performance of thin-walled square tubes with circular hole discontinuities under high-speed impact loading. *International Journal of Crashworthiness*, 27(6), 1622–1634. <https://doi.org/10.1080/13588265.2021.1981125>
- [18] Cheng, Q., Altenhof, W., & Li, L. (2006). Experimental investigations on the crush behaviour of AA6061-T6 aluminum square tubes with different types of through-hole discontinuities. *Thin-Walled Structures*, 44(4), 441–454. <https://doi.org/10.1016/j.tws.2006.03.017>
- [19] Elyasi, M., & Modanloo, V. (2024). Assessment of energy absorption and crushing performance of perforated thin-walled AA6061-O tubes with irregular holes under axial compression loading. *Arabian Journal for Science and Engineering*, 49(11), 15801–15812. <https://doi.org/10.1007/s13369-024-08779-z>
- [20] Gao, Q., Wang, L., Wang, Y., & Wang, C. (2016). Crushing analysis and multiobjective crashworthiness optimization of foam-filled ellipse tubes under oblique impact loading. *Thin-Walled Structures*, 100, 105–112. <https://doi.org/10.1016/j.tws.2015.11.020>
- [21] Li, X., Yin, Y., Zhu, X., Wang, R., Li, T., Zhang, Q., & Li, W. (2023). Performance of hollow and aluminum foam-filled multi-cell thin-walled aluminum alloy tubes (6063-T5) under axial impact. *Structures*, 47, 1803–1821. <https://doi.org/10.1016/j.istruc.2022.12.019>
- [22] Hou, S., Li, Q., Long, S., Yang, X., & Li, W. (2009). Crashworthiness design for foam filled thin-wall structures. *Materials & Design*, 30(6), 2024–2032. <https://doi.org/10.1016/j.matdes.2008.08.044>
- [23] Rouzegar, J., Assaee, H., Elahi, S. M., & Asiaei, H. (2018). Axial crushing of perforated metal and composite-

metal tubes. *Journal of the Brazilian Society of Mechanical Sciences and Engineering*, 40(7), 349. <https://doi.org/10.1007/s40430-018-1266-6>

[24] Mohamed Ismail, N. M. (2024). Performance analysis and optimization of square tubes with different shapes, sizes, and patterns of holes under axial compression loading. *International Journal of Crashworthiness*, 29(2), 247–273. <https://doi.org/10.1080/13588265.2023.2230644>